

AD



AD646173

Technical Report ECOM-2763

GALVANOSTATIC VOLTAGE TRANSIENTS OF
MAGNESIUM ANODES

by


Gabriel J. Di Masi

September 1966

ECOM

UNITED STATES ARMY ELECTRONICS COMMAND • FORT MONMOUTH, N.J.

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

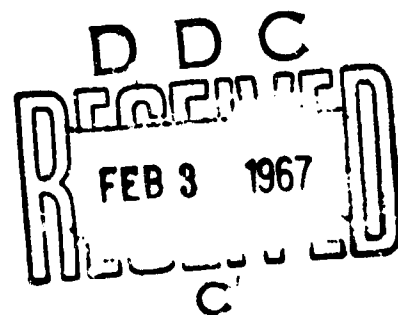

ARCHIVE COPY

ACCESSION NO.	
OPSTI	WHITE SECTION <input checked="" type="checkbox"/>
DDC	GRAY SECTION <input type="checkbox"/>
UNANNOUNCED	<i>for statement</i>
JUSTIFICATION	<i>for</i>
PL 18 SECTION/AVAILABILITY CODES	
DISC.	AVAIL. and/or SPECIAL
1	

NOTICES

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

The citation of trade names and names of manufacturers in this report is not to be construed as official Government indorsement or approval of commercial products or services referenced herein.

Disposition

Destroy this report when it is no longer needed. Do not return it to the originator.

TECHNICAL REPORT ECOM-2763

GALVANOSTATIC VOLTAGE TRANSIENTS OF
MAGNESIUM ANODES

by

Gabriel J. DiMasi

Power Sources Division
Electronic Components Laboratory

September 1966

DA Task ILO 13001 A 91A-19-00

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

U. S. ARMY ELECTRONICS COMMAND

FORT MONMOUTH, N. J.

Abstract

The voltage transient of the magnesium anode has been studied in 2 N and 6 N $\text{Mg}(\text{ClO}_4)_2$, MgBr_2 and MgCl_2 . In 6 N $\text{Mg}(\text{ClO}_4)_2$ the transient does not occur when a current is applied. In all other cases the transient polarization (ΔV_{max}) increased with increased applied current, but the transient time (τ) decreased. However, one exception is that in 2 N MgCl_2 ΔV_{max} increases with current, but τ remains fairly constant.

The effects of pretreating the electrode with a constant anodic current prior to pulsing have also been studied.

CONTENTS

	<u>Page</u>
ABSTRACT	11
INTRODUCTION	1
PREVIOUS INVESTIGATIONS	1
APPROACH	2
EXPERIMENTAL PROCEDURE	2
RESULTS	3
DISCUSSION OF RESULTS	5
RECOMMENDATIONS	5
REFERENCES	6

FIGURES

1. Constant Current Triggering Circuit	7
2. Voltage Transients - 2N $\text{Mg}(\text{ClO}_4)_2$	8
3. Voltage Transients - 2N MgBr_2	8
4. Voltage Transients - 2N MgCl_2	8
5. Voltage Transients - 6N $\text{Mg}(\text{ClO}_4)_2$	9
6. Voltage Transients - 6N MgBr_2	9
7. Voltage Transients - 6N MgCl_2	9

TABLES

I Effects of Electrolyte and Concentration - Applied Anodic Pulse - 15.4 ma/cm^2	3
II Effects of Electrolyte and Concentration - Applied Anodic Pulse - 10.8 ma/cm^2	4
III Effects of Pretreatment Current - 2N Concentration	4
IV Effects of Pretreatment Current - 6N Concentration	5

GALVANOSTATIC VOLTAGE TRANSIENTS OF MAGNESIUM ANODES

INTRODUCTION

During the past decade the implementation of magnesium anodes in primary batteries has received considerable attention. Primary cells, utilizing the magnesium anode, have two distinct advantages over batteries with conventional zinc anodes: Increased energy output per unit weight, and a longer shelf life when the corrosion has been greatly reduced. This has generally been achieved by using MgBr_2 , and $\text{Mg}(\text{ClO}_4)_2$ electrolytes at 2.0 to 2.5 N containing chromate inhibitors. However, an inherent phenomenon, associated with the magnesium anode is the occurrence of a voltage transient, when a load is applied to the electrochemical cell.

PREVIOUS INVESTIGATIONS

Roald and Beck¹ investigated the dissolution of magnesium in hydrochloric acid solutions ranging from 0.001 to 1.6 molar. They found that the corrosion rate increases both with increased concentration and with increased stirring. The dissolution rate measurements were explained by diffusion, with the proton being the rate-controlling species. Casey and Bergeron² measured the rate of corrosion in buffered solutions (at a pH = 2.0) of potassium and magnesium chloride. They found that the dissolution rate depends upon the concentration of the MgCl_2 electrolyte at ionic strengths greater than three. The corrosion process is described as a pure proton diffusion aided by internal dissolution of the film with increased concentration of the solution.

Glicksman³ studied the electrochemical behavior of Mg anodes at a current density of 2 ma/cm². The addition of metal ions such as mercurous, lead, aluminum, cadmium, platinum, cupric, and silver to MgBr_2 electrolyte changed the potential and the corrosion rate of the magnesium anode. Those metals, having a high exchange current for the hydrogen evolution reaction, accelerated the corrosion rate. Mercury decreases it. Apparently, these metal ions deposit on the electrode to form active centers for the hydrogen evolution reaction. Glicksman reports that the corrosion rate is a linear function of the applied current, and that the overall process is controlled by the diffusion rate of the proton through a porous magnesium oxide-hydroxide film on the anode.

Robinson and King⁴ found that when the applied anodic current is greater than the corrosion current, the magnesium electrode exhibits a voltage transient. Increased concentrations of MgBr_2 from 1.1 to 5 N decrease this phenomenon; increased currents decrease the transient time, but increase the transient polarization voltage. They explain it as a change in surface coverage that occurs when the Mg ion concentration increases at the anode. Thus, the hydroxyl ion concentration is depleted at the electrode. Thereafter, the halide ions attack the film, and the effective current density decreases, permitting the potential to return to a more negative potential. Recently, King⁵ has shown that the proportionality constant relating corrosion to applied current is the transference number of the anion.

In this laboratory, experiments⁶ have been conducted to reduce the initial transient polarization experienced by magnesium batteries. At the beginning

of the project the transient time of the batteries with an anode area of 6.5 cm² discharged under a ten-ohm load to a one-volt cutoff potential was 30 seconds. Increasing the concentration of Mg(ClO₄)₂ from 2 to 5 N reduced the transient time to 0.2 seconds, but the corrosion rate increased. Thus, to reduce the corrosion the cans were coated with palm oil or other compounds containing fatty acids or esters of fatty acids dissolved in benzene. Optimum results were obtained when a coating solution with one part of palm oil to 17 parts of benzene by weight was used. However, with this battery, designed to reduce the transient, a reduction in the hours of service was obtained.

APPROACH

The experimental investigation of the magnesium anode was conducted principally to determine the factors which affect the voltage transient. It is known from previous work⁴ and preliminary studies that electrolyte and electrolyte concentration influence the transient. Therefore, pure magnesium electrodes were studied in electrochemical cells of the type



in which the anion (X) was either ClO₄⁻, Cl⁻ or Br⁻ in two or six normal electrolyte concentrations.

Another condition observed in preliminary tests was that a certain amount of electrode corrosion must occur before a transient appears. A further ramification of this condition is that when an anodic current is applied to the magnesium electrode a certain period of zero current should be observed before the voltage transients are measured. When the electrode was in a conditioned state, anodic galvanostatic pulses were impressed on the magnesium electrode to obtain the voltage-time response which included the transient.

Subscribing to the belief that a surface film exists at the electrode, the amount of time (τ) required to reach the maximum transient polarization and ΔV_{max} , which are defined in Fig. 2, were used to characterize the transient. The reason for selecting τ to this point is based on Robinson's⁴ data in which he shows that if the current is removed before ΔV_{max} is reached, the potential returns to the open-circuit voltage. Thus, it is probable that there is no significant change in surface coverage before ΔV_{max} is reached. However, when the anodic current is shut off after the potential has passed ΔV_{max} , the electrode becomes temporarily more negative than at open circuit. It is likely that the surface film has been removed under this condition and that it formed again after the anodic current has been shut off.

EXPERIMENTAL PROCEDURE

Commercially pure magnesium electrodes were used in the electrochemical system previously described. The electrode was machined from a magnesium sheet with an area of 6.5 square centimeters. The amount of electrolyte used in each experiment was 75 ± 2 mls.

The cell utilized for these experiments was a three-compartment cell. The working electrode was placed in the center chamber, between two platinum counter electrodes. The two counter electrodes, also in the center, were used to obtain a more even distribution of current at the magnesium electrode. A saturated mercurous sulfate reference electrode was connected to the center chamber through a saturated potassium sulfate salt bridge.

Initially, the electrochemical system was conditioned with constant anodic currents of 1.5 or 15.4 ma/cm^2 for a period of ten minutes. There was a waiting period of five minutes between the conditioning current and the first anodic pulse, and for each subsequent pulse. The galvanostatic pulses were applied in a sequential order at 3.1, 6.15, 10.8, and 15.4 ma/cm^2 . The experiments were conducted at controlled room conditions ($70 \pm 2^\circ\text{F}$, 50% RH).

The measurement of the potential time oscillograms, at constant current, was performed with a triggering circuit (Fig. 1) in which a Tektronix Oscilloscope 561A was used in conjunction with a North Hills precision current source, Model CS-11. The relay was used to switch between the circuit having the 2-ohm load and the electrochemical cell. In this manner, the constant current source was brought to operating conditions using the 2-ohm circuit, eliminating the instrument delay due to warm-up time. Also, the circuit was designed to trigger the oscilloscope when the current transferal occurred. Therefore, a complete galvanostatic pulse which included open circuit, transient, and steady-state voltage was recorded by simply activating the camera shutter.

RESULTS

The voltage transients were compared at galvanostatic pulses of 3.1, 6.15, 10.8, and 15.4 ma/cm^2 . In 6 N $\text{Mg}(\text{ClO}_4)_2$ (Fig. 5) pure magnesium anode did not have a transient. In all other cases a transient voltage was observed. It was found that an increased galvanostatic pulse current produces a greater ΔV_{max} , but a smaller τ (Fig. 2, 3, 6, & 7). However, one exception occurs in 2 N MgCl_2 . In this case, an increased pulse current does not change τ , though ΔV_{max} increases. It is also pointed out that τ is less than in 2 N $\text{Mg}(\text{ClO}_4)_2$ and MgBr_2 .

TABLE I

EFFECTS OF ELECTROLYTE AND CONCENTRATION

APPLIED ANODIC PULSE - 15.4 ma/cm^2
PRETREATMENT - 1.5 ma/cm^2 for 10 Min.

ELECTROLYTE	CONCENTRATION	V_{MAX} (VOLTS)	τ (SEC)
$\text{Mg}(\text{ClO}_4)_2$	2N	0.28	0.053
	6N	c	0
MgBr_2	2N	0.68	0.040
	6N	0.20	0.094
MgCl_2	2N	0.20	0.02
	6N	0.30	0.16

TABLE II

EFFECTS OF ELECTROLYTE AND CONCENTRATION

APPLIED ANODIC PULSE - 10.8 ma/cm²
 PRETREATMENT - 1.5 ma/cm² for 10 Min.

ELECTROLYTE	CONCENTRATION	V _{MAX} (VOLTS)	T (SEC)
Mg(ClO ₄) ₂	2N	0.20	0.075
	6N	0	0
MgBr ₂	2N	0.55	0.05
	6N	0.18	0.14
MgCl ₂	2N	0.18	0.025
	6N	0.20	0.25

At 2 N concentrations, T (Tables I & II) decreases according to the electrolyte in this manner

$$T_{\text{ClO}_4^-} > T_{\text{Br}^-} > T_{\text{Cl}^-}$$

and ΔV_{max} is

$$\Delta V_{\text{Br}^-} > \Delta V_{\text{ClO}_4^-} > \Delta V_{\text{Cl}^-}.$$

However, in 6 N solutions the trend is not the same, but shows a complete reversal in which

$$T_{\text{Cl}^-} > T_{\text{Br}^-}$$

and

$$\Delta V_{\text{Cl}^-} > \Delta V_{\text{Br}^-}.$$

Thus, the trend in both T and ΔV_{max} changes according to the electrolyte concentration.

TABLE III

EFFECTS OF PRETREATMENT CURRENT

APPLIED ANODIC PULSE - 15.4 ma-cm²
 2N CONCENTRATION
 PRETREATMENT TIME - 10 Min.

ELECTROLYTE	PRETREATMENT CURRENT DENSITY	V _{MAX} (VOLTS)	T (SEC)
Mg(ClO ₄) ₂	1.5 ma/cm ²	0.28	0.053
	15.4 ma/cm ²	0.20	0.06
MgBr ₂	1.5 ma/cm ²	0.68	0.04
	15.4 ma/cm ²	0.55	0.08
MgCl ₂	1.5 ma/cm ²	0.20	0.02
	15.4 ma/cm ²	0.85	2.0

TABLE IV

EFFECTS OF PRETREATMENT CURRENT

APPLIED ANODIC PULSE - 15.4 ma/cm^2
 6N CONCENTRATION
 PRETREATMENT TIME - 10 Min.

ELECTROLYTE	PRETREATMENT CURRENT DENSITY	V_{MAX} (VOLTS)	τ (SEC)
$\text{Mg}(\text{ClO}_4)_2$	1.5 ma/cm^2	0	0
	15.4 ma/cm^2	0	0
MgBr_2	1.5 ma/cm^2	0.18	0.14
	15.4 ma/cm^2	0.15	0.09
MgCl_2	1.5 ma/cm^2	0.20	0.25
	15.4 ma/cm^2	0.12	0.12

The effects of pretreatment current are presented in Tables III and IV. In all cases at 2 N for a pretreatment time of ten minutes, the delay time at the higher pretreatment current is greater than at the lower, but ΔV_{max} does not show a constant trend. In 6 N electrolytes a reverse trend is observed whereas τ decreases at the higher pretreatment current.

DISCUSSION OF RESULTS

The effects of current density, electrolyte, concentration, and pretreatment are reproducible and have a maximum deviation of $\pm 5\%$. The general effects of current density on τ and ΔV_{max} give greater evidence for accepting the dissolution of the anodic film as the controlling process before a steady-state potential is reached. The mechanism which describes this film breakdown has not been established.

The effects of anion and concentration are presented, but no comments as to the significance of the results can be made without further study. Pretreating the magnesium electrode with an anodic constant current has produced results which may be partially the effects of pH. Calculations have shown that at pretreatment current densities of 1.54 and 15.4 ma/cm^2 excessive amounts of hydroxyl ions are formed causing $\text{Mg}(\text{OH})_2$ to precipitate. This is the case, both in 2 N electrolytes at $\text{pH} = 8.45$ and in 6 N electrolytes at $\text{pH} = 8.24$. During pretreatment at open-circuit potential a $\text{Mg}(\text{OH})_2$ film is formed by corrosion. This film is not formed during the anodic pretreatment because transients were observed only after a waiting period at open circuit potential.

RECOMMENDATIONS

1. A study of the pH effects on the voltage transient should be undertaken. These measurements should be correlated with the corrosion rate and the corrosion pattern at the magnesium anode. Estimates of the surface roughness should also be made.

2. To determine the effects of diffusion on the transient, the electrolyte should be stirred.

3. Glicksman³ has found that amalgamating magnesium with small quantities of mercury reduces its corrosion rate. Since corrosion initiates conditions favorable for the occurrence of the transient a less corrosive electrode should be explored.

REFERENCES

1. B. Roald and N. Beck, "Electrochemical Society Journal," 98, 277 (1951).
2. E. J. Casey and R. E. Bergeron, "Canadian Journal of Chemistry," 31, 840 (1953).
3. R. Glicksman, "Electrochemical Society Journal," 106, 83 (1959).
4. J. L. Robinson and P. F. King, "Electrochemical Society Journal," 108, 36 (1961).
5. P. F. King, "Electrochemical Society Journal," 113, 536 (1966).
6. D. Wood and J. Hovendon, "Magnesium Dry Cell Batteries," Power Sources Conference, 19th Annual Proceedings (May 1965).

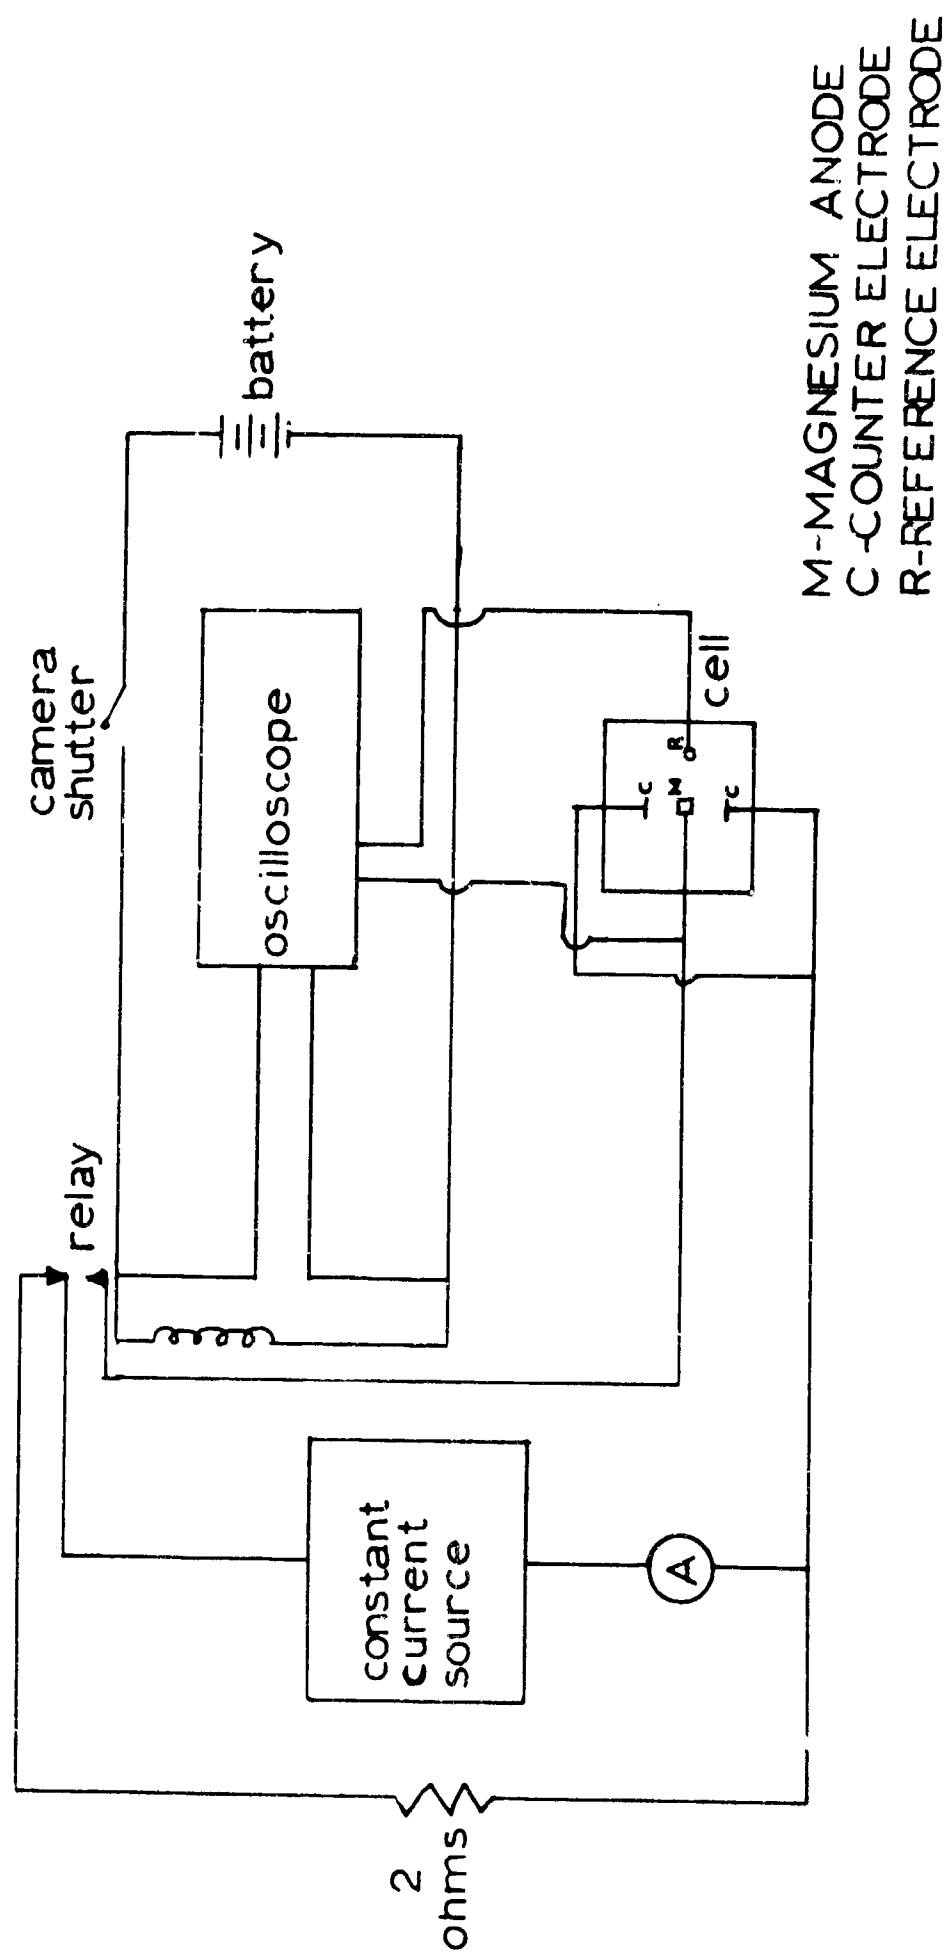


FIG.1 CONSTANT CURRENT TRIGGERING CIRCUIT

ANODIC VOLTAGE TRANSIENTS
 PURE Mg - 2N ELECTROLYTE
 PRETREATMENT - 15 mA/cm² FOR 10 MIN

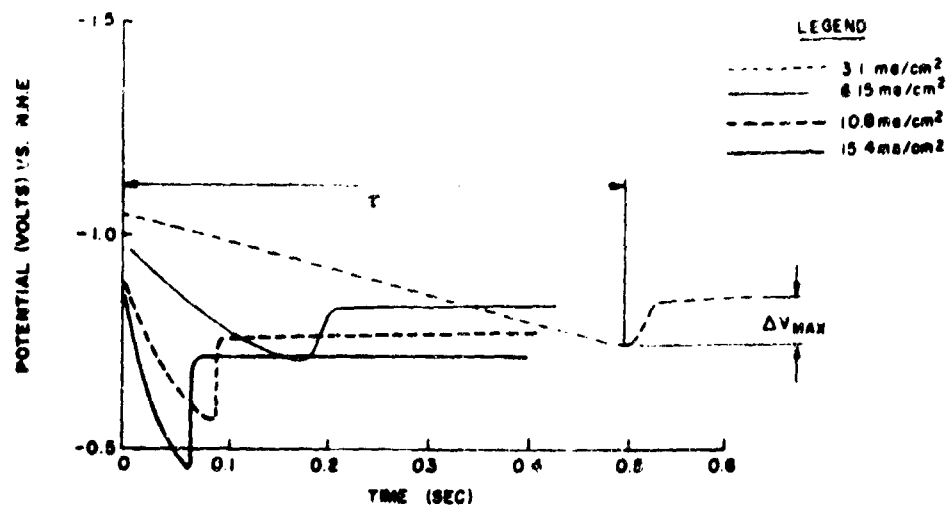


FIG. 2 $Mg(ClO_4)_2$
 O.C.V. = -1.11 VOLTS

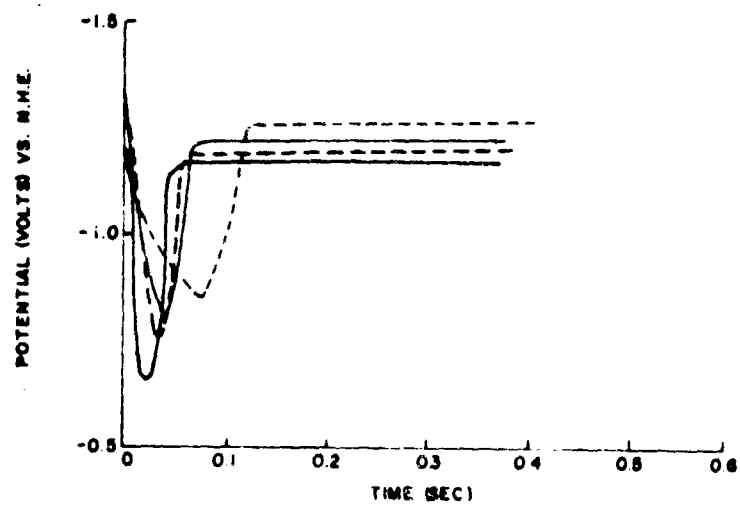


FIG. 3 $MgBr_2$
 O.C.V. = -1.33 VOLTS

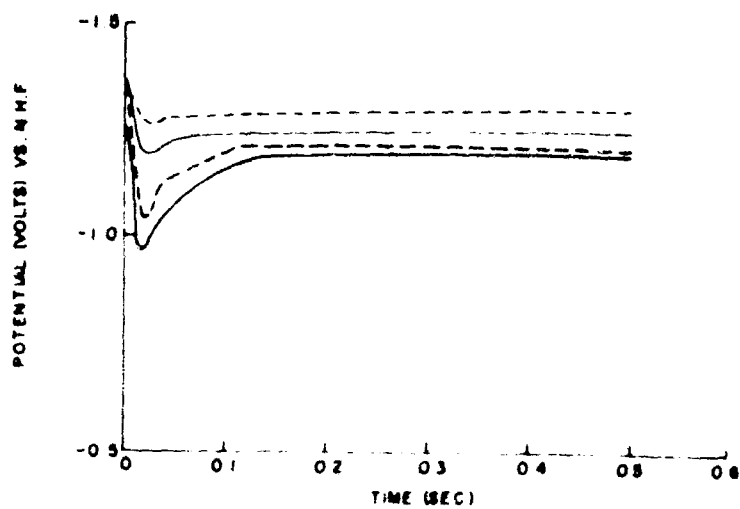


FIG. 4 $MgCl_2$
 O.C.V. = -1.43 VOLTS

ANODIC VOLTAGE TRANSIENTS
 PURE Mg-SN ELECTROLYTE
 PRETREATMENT - 1.6 mC/cm^2 FOR 10 MIN.

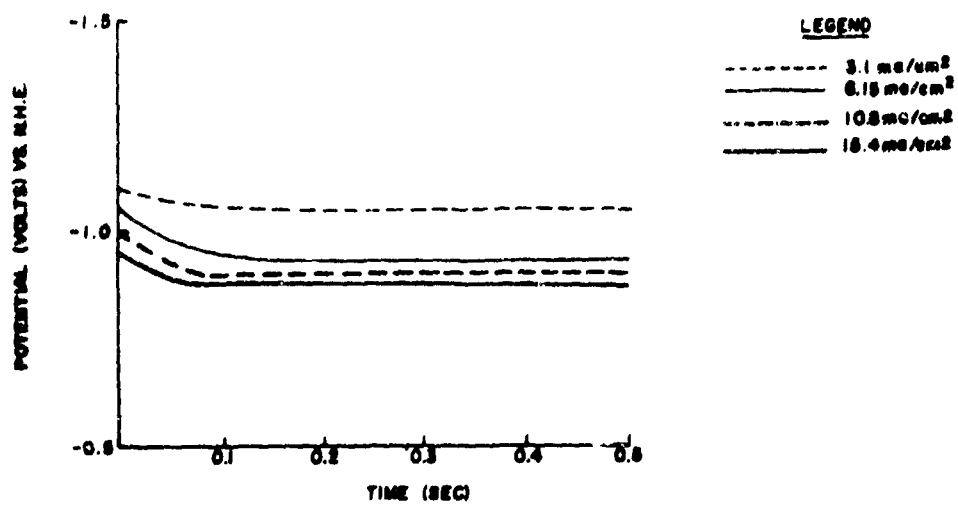


FIG. 6 $\text{Mg}(\text{ClO}_4)_2$
 O.C.V. = -1.2 VOLTS

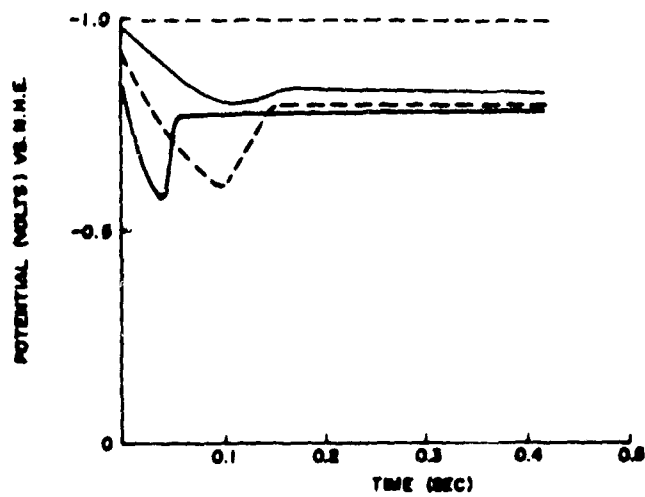


FIG. 6 MgBr_2
 O.C.V. = -1.00 VOLTS

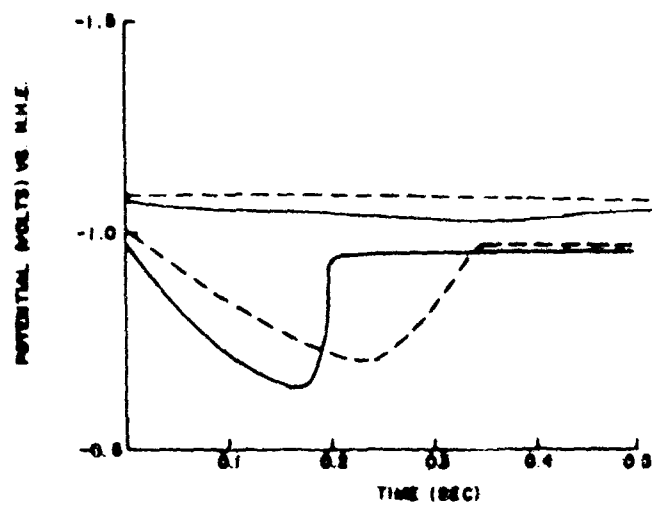


FIG. 7 MgCl_2
 O.C.V. = -1.15 VOLTS

DOCUMENT CONTROL DATA - R&D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1 ORIGINATING ACTIVITY (Corporate author) U.S. Army Electronics Command Fort Monmouth, N.J. 07703		2a REPORT SECURITY CLASSIFICATION Unclassified	
		2b GROUP	
3 REPORT TITLE GALVANOSTATIC VOLTAGE TRANSIENTS OF MAGNESIUM ANODES			
4 DESCRIPTIVE NOTES (Type of report and inclusive dates) Technical Report			
5 AUTHOR(S) (Last name, first name, initial) DiMasi, Gabriel J.			
6 REPORT DATE September 1966		7a TOTAL NO. OF PAGES 9	7b NO. OF REFS 6
8a CONTRACT OR GRANT NO.		9a ORIGINATOR'S REPORT NUMBER(S) ECON-2763	
b PROJECT NO. 110 13001 A 91A		9b OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
c Task No. -19			
d Subtask No. 00			
10 AVAILABILITY/LIMITATION NOTICES Distribution of this document is unlimited.			
11 SUPPLEMENTARY NOTES		12 SPONSORING MILITARY ACTIVITY Commanding General U.S. Army Electronics Command Fort Monmouth, N.J. AMSEL-KL-PB	
13 ABSTRACT <p>The voltage transient of the magnesium anode has been studied in 2 N and 6 N $Mg(ClO_4)_2$, $MgBr_2$ and $MgCl_2$. In 6 N $Mg(ClO_4)_2$ the transient does not occur when a current is applied. In all other cases the transient polarization (ΔV_{max}) increased with increased applied current, but the transient time (Δt) decreased. However, one exception is that in 2 N $MgCl_2$ ΔV_{max} increases with current, but remains fairly constant.</p> <p>The effects of pretreating the electrode with a constant anodic current prior to pulsing have also been studied.</p> <p style="text-align: right;"><i>Heuts</i></p>			

KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Corrosion Half-Cell Studies Magnesium Anode Pretreatment Effects Voltage-Time Curves Transient Polarization Electrolyte Effects						

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (either by the originator or by the sponsor), also enter this number(s).

10. **AVAILABILITY LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (paying for) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, roles, and weights is optional.